

Structural investigations on ϵ -FeGe at high pressure and low temperature

H. Wilhelm,¹ M. Schmidt,² R. Cardoso-Gil,² U. Burkhardt,² M. Hanfland,³ U. Schwarz,² and L. Akselrud⁴

¹*Diamond Light Source Ltd., Chilton, Didcot, Oxfordshire, OX11 0DE, United Kingdom*

²*Max Planck Institut für Chemische Physik fester Stoffe, Nöthnitzer Str. 40, 01187 Dresden, Germany*

³*European Synchrotron Radiation Facility, 38043 Grenoble, Cedex, France*

⁴*Ivan Franko Lviv National University, Kyrylo and Mephodiy Street 6, 79005 Lviv, Ukraine*

The structural parameters of ϵ -FeGe have been determined at ambient conditions using single crystal refinement. Powder diffraction have been carried out to determine structural properties and compressibility for pressures up to 30 GPa and temperatures as low as 82 K. The discontinuous change in the pressure dependence of the shortest Fe-Ge interatomic distance might be interpreted as a symmetry-conserving transition and seems to be related to a magnetic phase boundary line.

INTRODUCTION

Binary transition metal compounds crystallizing in the $B20$ structure (space group $P2_13$) [1, 2] show a variety of interesting physical properties ranging from a narrow-gapped semiconductor (FeSi) to diamagnetic (CoSi) or paramagnetic (FeGe) metal. In the latter case recent experiments have shown that the helical ordering temperature ($T_C = 280$ K at ambient pressure) can be suppressed by the application of external pressure [3]. Furthermore, anomalies in internal structural parameters in cubic FeGe (ϵ -FeGe) for isothermal compression seem to be related to the magnetic phase boundary line. Here we present single crystal data at ambient conditions as well as in detail the results of the powder diffraction data at high pressure and temperatures as low as 82 K.

SAMPLE GROWTH AND CHARACTERIZATION

Single crystals of ϵ -FeGe were grown by chemical vapor transport using iodine as agent [4] in a homemade two zone furnace. ϵ -FeGe crystallized very slowly by an endothermal transport reaction from 850 K to 810 K although the transport was made perpendicular to the tube axis [5]. The resulting crystals had a volume of less than 1 mm³. Pieces used in the subsequent experiments were examined thoroughly by various X-ray techniques and electron-beam microanalysis.

The wavelength-dispersive-X-ray-analysis (WDX) performed on a microprobe (CAMECA SX100, W-cathode) confirms the ratio Fe:Ge = 1:1 of the crystals and X-ray spectra excited by electron beam (25 keV, 20 nA) showed only lines of both elements. The evaluation of the background intensities at energies of Si- K and I- L -lines allowed us to exclude impurity concentrations larger then 0.08 wt.% for both elements involved in the preparation process. Microstructures prepared from crystals by metallographic methods contained small, disoriented areas which show unusual strong orientation in the scanning electron microscope images using back-scattered electron (BSE) contrast as well as in polarized light of the light

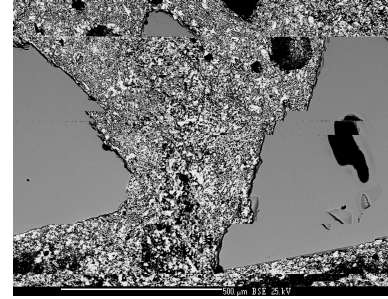


FIG. 1: Microstructure of well-faceted ϵ -FeGe-sample (scanning electron microscope image, BSE contrast) is dominated by single crystalline area (homogenous grey) and cavity (black) at the center. A small, disoriented area (darker grey) next to the central hole shows weak contrast in the BSE image but no significant differences in composition is found by WDX measurements.

microscope (cf. Fig. 1).

SINGLE CRYSTAL STRUCTURE DETERMINATION

The crystal structure of ϵ -FeGe was solved and refined on single crystal intensity data (Rigaku R-Axis Spider, Ag- $K\alpha$ radiation, $\lambda = 56.080$ pm, rotating anode-micro source, with mirror optic, ω -scan, $\Delta\omega = 1.0^\circ$, 160 images; $2\Theta_{max} = 122.6^\circ$, empirical absorption correction). For the structure refinement a full-matrix least squares on F^2 on eight parameter was performed using SHELXL-97 [6].

TABLE I: Details of the crystal structure analysis of ϵ -FeGe at ambient pressure and $T = 295$ K.

Density (g cm ⁻³)	8.22
μ (cm ⁻¹)	219
measured and unique reflections	3680; 1025
obs. reflections $> 4.0 \sigma(Fo)$	1001
R_{int}	0.018
$R1; wR2$	0.020; 0.026
Goof=S	1.209
$\Delta\rho_{max}; \Delta\rho_{min}$ (e10 ⁶ pm ³)	2.05; -1.01

TABLE II: Anisotropic displacement parameter U_{ij} (in pm²) for ϵ -FeGe. The U_{eq} is defined as one third of the orthogonalized U_{ij} tensor.

	$U_{11} = U_{22} = U_{33}$	$U_{23} = U_{13} = U_{12}$	U_{eq}
Fe	57(2)	-6(1)	57(2)
Ge	55(2)	0(1)	55(2)

A summary of the refinement data is given in Tab. I and II. The lattice parameter were determined from powder data on 12 reflections with the program package CSD [7] (image plate Guinier camera HUBER G670, Co- $K\alpha_1$, $\lambda = 178.8965$ pm, LaB₆ ($a = 415.692$ pm) as internal standard, $T = 295$ K). All structural parameter are given in Tab. III.

In the $B20$ structure (space group $P2_13$, No. 198, $Z = 4$) both atoms occupy $4a$ (x, x, x) Wyckoff positions (Fig. 2). In a compound AB crystallizing in the ideal $B20$ structure ($x_A = 0.1545$, $x_B = 1 - x_A$) both atoms have a seven-fold coordination which lies between that of the two simplest binary cubic structures NaCl (CN = 6) and CsCl (CN = 8). ϵ -FeGe however, attains a distorted rock-salt structure where the atoms are slightly shifted from their ideal position ($x_{Fe} = 0.13522(2)$ and $x_{Ge} = 0.84186(1)$). This results in one short Fe-Ge distance, $d_1 = 238.78$ pm, along the trigonal axis pertinent to the Fe atom as well as two longer ones, $d_2 = 244.57$ pm, and $d_3 = 264.45$ pm, between the three second and three third-nearest neighbors, respectively (see Fig. 3). Thus, the coordination sphere of Fe is build up of seven Ge atoms describing a strong distorted mono capped trigonal prism.

POWDER DATA AT HIGH PRESSURE

The structural evolution with pressure at different temperatures was determined by angle-dispersive X-ray diffraction experiments at the beamline ID09 at the European Synchrotron Radiation Facility. The diffraction pattern were collected at a wavelength of $\lambda = 41.254$ pm during a 10 s exposure time with an image plate. For these measurements well ground and annealed powder (at 670 K for two days) was loaded in a diamond-anvil cell. He-

TABLE III: Structural parameters of ϵ -FeGe at ambient conditions and for comparison data of ϵ -FeSi taken from Ref. [9]. In the standard setting the fractional coordinates are $x_{Fe} = 0.38522(2)$, $x_{Ge} = 0.09186(1)$ for ϵ -FeGe and $x_{Fe} = 0.38650(2)$, $x_{Si} = 0.09262(5)$ for ϵ -FeSi. B denotes either Ge or Si.

	ϵ -FeGe	ϵ -FeSi
a (pm)	469.95(2)	449.5(2)
V_0 (10 ⁶ pm ³)	103.79(1)	90.8
x_{Fe}	0.13522(2)	0.13650(2)
x_B	0.84186(1)	0.84262(5)
d_1 (pm)	238.78(2)	228.8
d_2 (pm)	244.57(1)	234.6
d_3 (pm)	264.45(1)	251.98
d_{Fe-Fe} (pm)	288.11(1)	275.6
d_{B-B} (pm)	291.13(1)	278.3

TABLE IV: Bulk modulus B_0 , and its pressure derivative B' of ϵ -FeGe obtained from a fit of the Murnaghan EOS to the $V(p)$ data.

T (K)	B_0 (GPa)	B'
295	130(1)	4.7(1)
230	135(1)	4.7(1)
82	147(3)	4.4(2)

lium was used as pressure medium and the pressure was determined via the fluorescence peaks of SrB₄O₇:Sm²⁺ [8].

Figure 4(a) shows two examples of a full profile structural refinement of the diffraction pattern recorded at 82 K. The intensities can be very well refined though with little less precision at the highest pressure. Thus, the fractional atomic parameter x_{Fe} and x_{Ge} , and hence the interatomic distances could be deduced. The refinement of the diffraction pattern measured at 82 K and 230 K revealed clear indications that the shortest interatomic Fe-Ge distance, d_1 , which is parallel to $[111]$, changes its pressure dependence discontinuously (Fig. 4(b) and Fig. 5(a)). The extrapolation of the low-pressure $d_1(p)$ behavior for 82 K and 230 K described by an appropriate equation-of-state (EOS) clearly fails to account for the pressure dependence above 15.8 GPa and 12 GPa, respectively. These anomalies in $d_1(p)$ agree remarkably well with the $T_C(p)$ -phase boundary deduced from the electrical resistivity measurements reported in Ref. [3]. The two remaining Fe-Ge distances as well as all distances at room temperature (Fig. 5(b)) decrease smoothly with pressure and no anomaly is seen within the error bars.

The $V(p)$ dependencies of ϵ -FeGe at all investigated temperatures revealed no discontinuous pressure dependence and that the compression is reversible (cf. insets to Figs. 4(b) and 5). All $V(p)$ can be described by a Murnaghan EOS [10]. The resulting fit parameters are

given in Tab. IV. The bulk modulus of ϵ -FeGe is considerably smaller than that of ϵ -FeSi which is ranging from $B_0 = 160(1)$ GPa ($B' = 4.0$) [11] to 209(6) GPa ($B' = 5.3$) [12]. A simple comparison of the unit-cell volume and using the compressibility of ϵ -FeGe shows that ϵ -FeGe attains the same unit-cell volume as ϵ -FeSi at about 25 GPa. Theoretical studies on ϵ -FeSi predict a phase transformation to the $B2$ structure (CsCl-type) at about 13 GPa [13] or in the range of 30 to 40 GPa [14]. On the other hand, no phase transformation in ϵ -FeSi has been found up to 50 GPa [12]. Thus, more structural information at pressures well above 30 GPa is needed to resolve the stability of ϵ -FeGe.

We acknowledge W. Schnelle for characterizing the samples by magnetic measurements and H. Borrmann for single crystal data collection. We are grateful to R. Demchnya and A. Wosylus for their commitment during the high pressure X-ray experiments.

[1] B. Borén, Arkiv Kemi Min. Geol. 11A, 1 (1933).

[2] L. Pauling and A. M. Soldate, Acta Crystallogr. **1**, 212 (1948).

[3] P. Pedrazzini, H. Wilhelm, D. Jaccard, T. Jarlborg, M.

Schmidt, M. Hanfand, L. Akselrud, H. Q. Yuan, U. Schwarz, Yu. Grin, and F. Steglich, Phys. Rev. Lett. **98**, 047204 (2007).

[4] M. Richardson, Acta Chem. Scand. **21**, 2305 (1967).

[5] V. Krämer, R. Nitsche, and M. Schumacher, J. Cryst. Growth **24/25**, 179 (1974).

[6] G. M. Sheldrick; SHELXL-97, Program for the crystal structure refinement, University of Göttingen, Germany, 1997, release 97-2.

[7] L. G. Akselrud, P. Yu. Zavalli, Yu. Grin, V. K. Pecharsky, B. Baumgartner, and E. Wölfel, Mater. Sci. Forum **133-136**, 335 (1993).

[8] J. Leger, C. Chateau, and A. Lacam, J. Appl. Phys. **68**, 2351 (1990); F. Datchi, R. LeToullec, and P. Loubeyre, *ibid* **81**, 3333 (1997).

[9] R. Wartchow, S. Geringhausen, and M. Binnewies, Z. Kristallogr. **212**, 320 (1997).

[10] F. D. Murnaghan, Proc. Natl. Acad. Sci. USA **30**, 244 (1944).

[11] I. G. Wood *et al.*, J. Phys.: Condens. Matter **7**, L475 (1995).

[12] E. Knittle and Q. Williams, Geophys. Res. Lett. **22**, 445 (1990).

[13] L. Vočadlo, G. D. Price, and I. G. Wood, Acta Crystallogr. B **55**, 484 (1999).

[14] R. Caracas and R. Wentzcovitch, Geophys. Res. Lett. **31**, L20603 (2004).

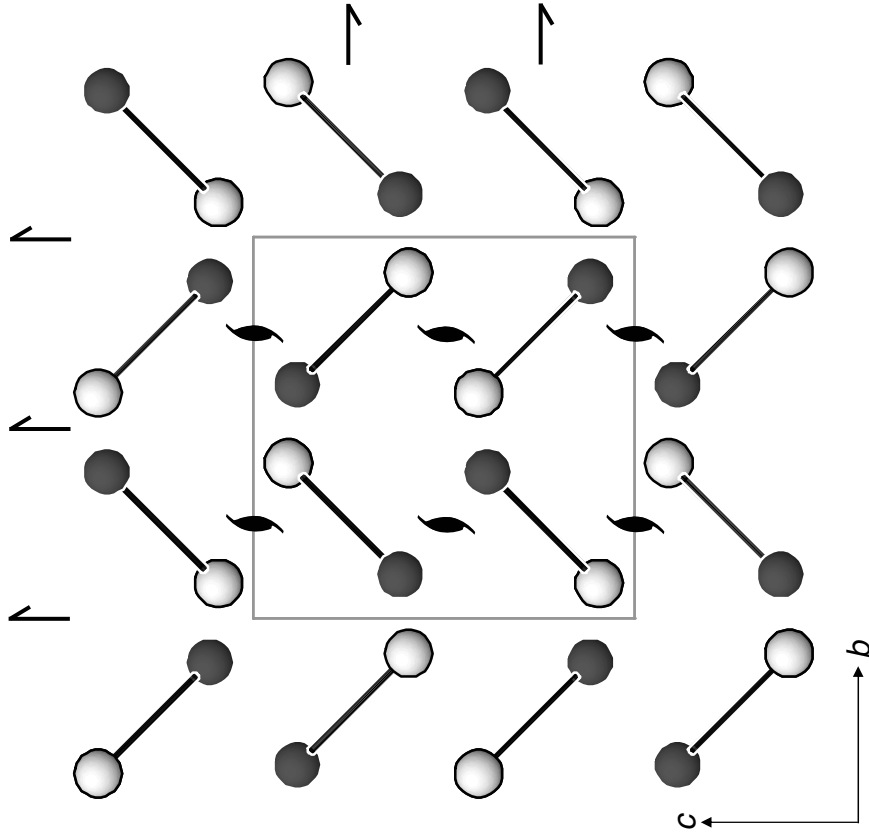


FIG. 2: Projection of the crystal structure of ϵ -FeGe along $[100]$. The symbols show the position of the 2_1 screw axis. The lines indicate the shortest Fe-Ge distance.

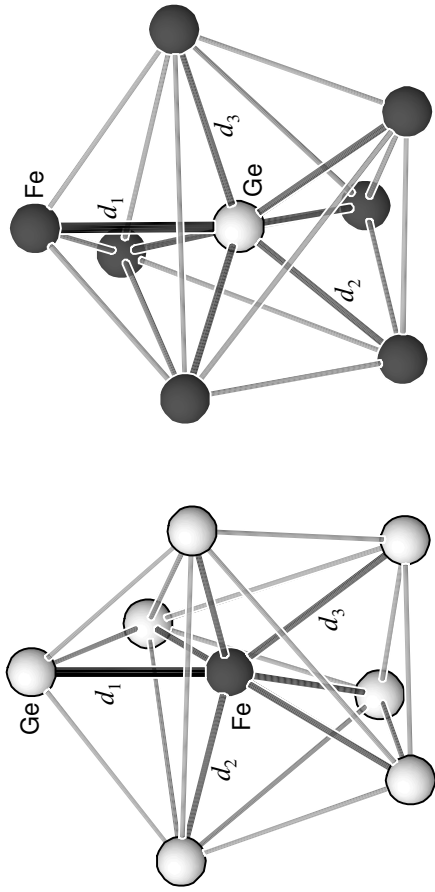


FIG. 3: Coordination polyhedron of Fe (left) and Ge (right). The shortest Fe-Ge distance is d_1 .

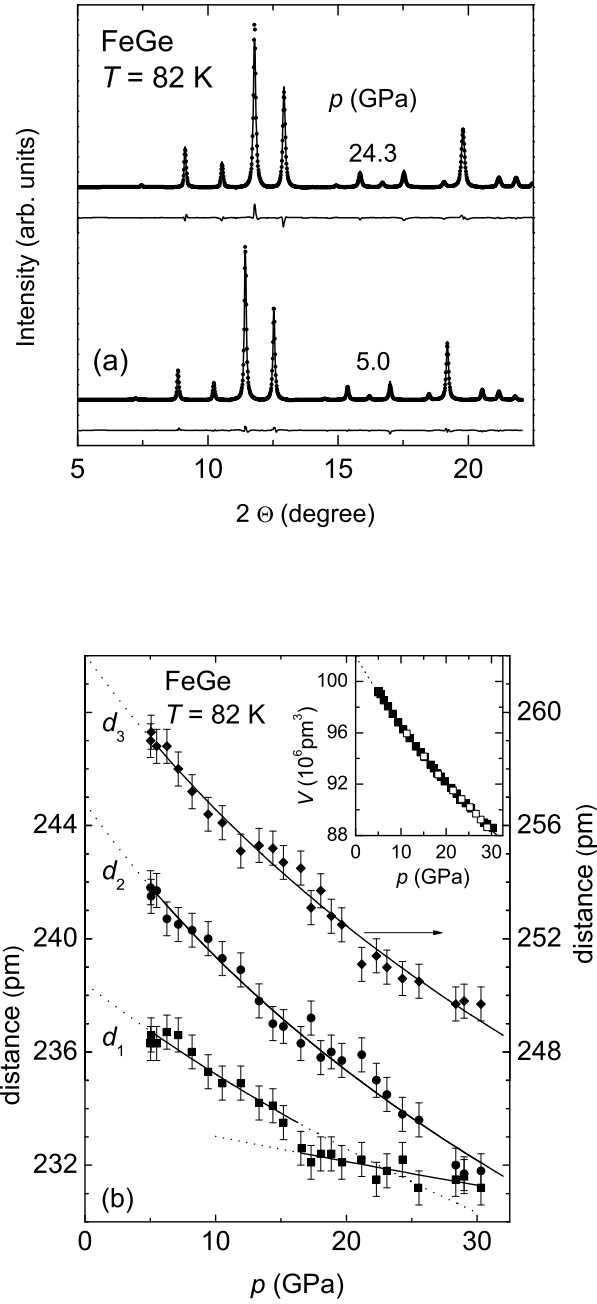


FIG. 4: (a) Diffraction pattern recorded at 82 K at different pressures. The difference between raw and fitted data is also shown. (b) Pressure dependence of the interatomic Fe-Ge distances d_1 and d_2 (left scale) and d_3 (right scale). The lines represent a Murnaghan EOS fit to the data. In $d_1(p)$ a discontinuity at about 15 GPa indicates a subtle change in the distances. Error bars represent 3σ . Inset: $V(p)$ data and EOS fit. Open symbols represent data obtained on pressure release.

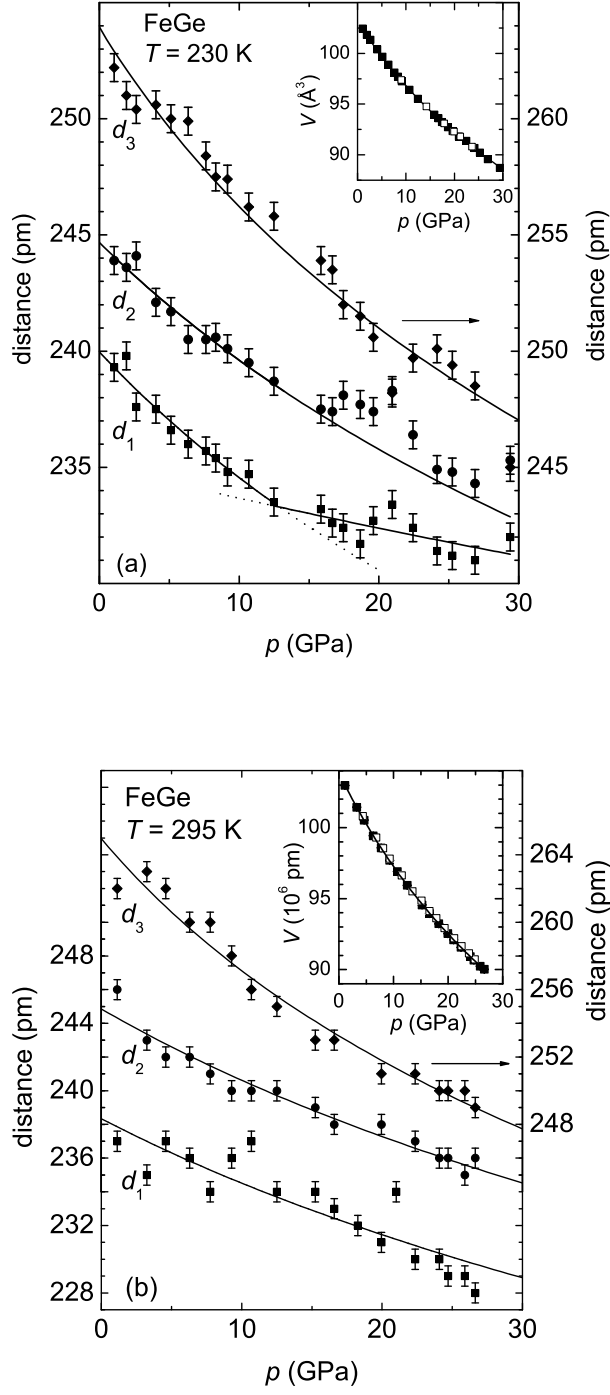


FIG. 5: Pressure dependence of the interatomic Fe-Ge distances d_1 and d_2 (left scale) and d_3 (right scale). Error bars represent 3σ . The lines represent a Murnaghan EOS fit to the data. (a) $T = 230$ K data set, where $d_1(p)$ shows a discontinuity at about 12 GPa. (b) $T = 295$ K data set, where no anomaly in $d_1(p)$ is observed. Insets: $V(p)$ data and EOS fit. Data obtained on decreasing pressure are shown as open symbols.